

# RAMAX® 2

Prehardened stainless holder steel

COLD WORK

PLASTIC MOULDING

HOT WORK

HIGH PERFORMANCE STEEL



This information is based on our present state of knowledge and is intended to provide general notes on our products and their uses.  
It should not therefore be construed as a warranty of specific properties of the products described or a warranty for fitness for a particular purpose.

## General

Ramax 2 is a new chromium alloyed stainless holder steel, which is supplied in the hardened and tempered condition.

Ramax 2 is characterized by

- Excellent machinability
- Good corrosion resistance
- Good hardenability
- Uniform hardness in all dimensions
- Good indentation resistance

These properties combine to give a steel with outstanding production performance. The practical benefits of **good corrosion resistance** in a holder steel can be summarized as follows:

- Lower mould maintenance cost
- Lower production costs since water cooling channels are unaffected by corrosion, ensuring consistent cycle time

The practical benefits of the **excellent machinability** can be summarized as follows:

- Lower mould production costs due to:
  - less wear of the cutting edges in the milling and drilling operations
  - increased cutting speed can be used providing for a shorter machining time

|                    |                                    |
|--------------------|------------------------------------|
| Typical analysis % | Cr-Ni-Mo-V alloyed +Sulphur        |
| Delivery condition | Hardened and tempered to ~ 340 HB  |
| Colour code        | Black/brown with white line across |

## Applications

- Holders/bolsters for plastic moulds.
- Plastic and rubber moulds with low requirements on polishability
- Dies for plastic extrusion
- Constructional parts

## Properties

### PHYSICAL DATA

Hardened and tempered to 350 HB. Data at room and elevated temperatures.

| Temperature  | 20°C<br>(68°F)                    | 200°C<br>(390°F)                                  |
|--|-----------------------------------|---|
| Density<br>kg/m <sup>3</sup><br>lbs/in <sup>3</sup>                      | 7 700<br>0,280                    | –<br>–  |
| Modulus of elasticity<br>Mpa<br>psi                                      | 215 000<br>31,2 x 10 <sup>6</sup> | 205 000<br>29,7 x 10 <sup>6</sup>                 |
| Coefficient of thermal expansion<br>per °C from 20°C<br>per °F from 68°F | –<br>–                            | 10,8 x 10 <sup>-6</sup><br>6,0 x 10 <sup>-6</sup> |
| Thermal conductivity*<br>W/m °C<br>Btu in/ft <sup>2</sup> h °F           | –<br>–                            | 24<br>166   |
| Specific heat capacity<br>J/kg °C<br>Btu/lb°F                            | 460<br>0,110                      | –   |

\*Thermal conductivity is very difficult to measure. The scatter can be as high as ±15%

### TENSILE STRENGTH

Approximate values. Samples were taken from a bar 255 x 60 mm (10 x 2,4") in length direction.

Hardness: 350 HB.

| Testing temperature                            | 20°C<br>(68°F)                  | 200°C<br>(390°F)                |
|--|---------------------------------|---------------------------------|
| Tensile strength Rm,<br>MPa<br>psi             | 1 140<br>1,65 x 10 <sup>5</sup> | 1 020<br>1,48 x 10 <sup>5</sup> |
| Yield strength Rp <sub>0,2</sub><br>MPa<br>psi | 990<br>1,44 x 10 <sup>5</sup>   | 920<br>1,33 x 10 <sup>5</sup>   |
| Reduction of area Z, %                         | 46                              | 48                              |
| Elongation A <sub>5</sub> , %                  | 12                              | 10                              |

Note: The high sulphur content gives lower mechanical properties in the transverse compared with the longitudinal direction.



Holder plate

## TOUGHNESS/DUCTILITY


Ramax 2 has much higher toughness/ ductility compared to other stainless holders of W.-Nr.1.2085 type.

Approximate room temperature impact strength in the longitudinal direction in the centre is given in the graph below.

*Specimen size:* 7 x 10 x 55 mm (0,27 x 0,4 x 2,2") unnotched.

*Delivery condition:* ~350 HB

Unnotched impact energy, J

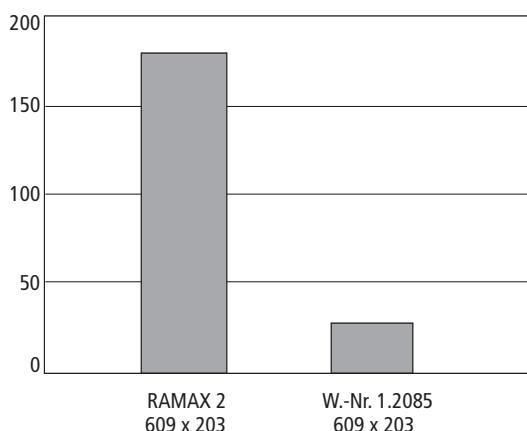

*Note:* The high sulphur content gives lower mechanical properties in the transverse compared with longitudinal direction.


## CORROSION RESISTANCE

Holders made from Ramax 2 will have good resistance to corrosion caused by humid working and storage conditions and when moulding corrosive plastics under normal production conditions

In the graph below values from potentiodynamic polarization curves has been evaluated to show the difference in general corrosion resistance between Ramax 2 and W.-Nr.1.2085.

*Specimen size:* 20 x 15 x 3 mm (0,8 x 0,6 x 0,12")

Relative corrosion resistance %

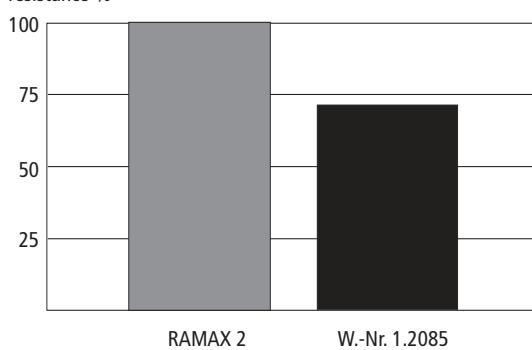

## Heat treatment

Ramax 2 is intended for use in the as-delivered condition i.e. hardened and tempered to 350 HB.

When the steel is to be heat treated to higher hardness, instructions below are to be followed.

*Note;* however that an increased hardness yields a lower toughness.

### SOFT ANNEALING

Protect the steel and heat through to 740°C (1365°F). Cool at 15°C (30°F) per hour to 550°C (1020°F), then freely in air.

### STRESS RELIEVING

After rough machining the tool should be heated through to max. 530°C (985°F), holding time 2 hours, then cool freely in air.

### HARDENING

*Note:* The steel should be annealed before hardening.

*Preheating temperature:* 500–600°C (930–1110°F).  
*Austenitizing temperature:* 980–1020°C (1795–1870°F).

The steel should be heated through to the austenitizing temperature and held at temperature for 30 minutes.

*Protect the tool against decarburization and oxidation during the hardening process.*

### QUENCHING MEDIA


- Oil
- Fluidized bed or salt bath at 250–550°C (480–1020°F), then cool in air blast
- Vacuum with sufficient positive pressure
- High speed gas/circulating atmosphere

In order to obtain the optimum properties, the cooling rate should be as fast as possible within acceptable distortion limits. Temper the tool as soon as its temperature reaches 50–70°C (120–160°F).

**TEMPERING**

Choose the tempering temperature according to the hardness required by reference to the tempering graph. Temper twice with intermediate cooling to room temperature. Lowest tempering temperature 250°C (480°F). Holding time at temperature minimum 2 hours.

*Austenitizing temperature: 1000°C (1830°F), 30 min.  
Holding time: 2 + 2h*

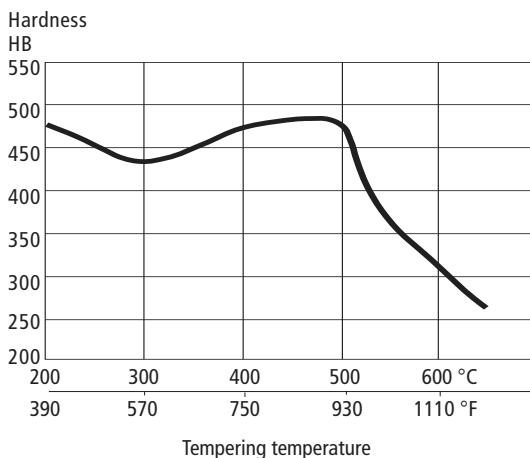

*Machinability is a critical property during manufacturing of holder plates.*

**Machining**

The cutting data below are to be considered as guiding values which must be adapted to existing local conditions. More information can be found in the Uddeholm publication "Cutting data recommendation".

**TURNING**

| Cutting data parameters                     | Turning with carbide               |                                       | Turning with high speed steel<br>Fine turning |
|---|------------------------------------|---------------------------------------|---|
|   | Rough turning                      | Fine turning                          |   |
| Cutting speed ( $v_c$ )<br>m/min.<br>f.p.m. | 110–160<br>360–525                 | 160–210<br>525–690                    | 18–23<br>59–75                                |
| Feed ( $f$ )<br>mm/r<br>i.p.r.              | 0,2–0,4<br>0,008–0,016             | 0,05–0,2<br>0,002–0,008               | 0,05–0,3<br>0,002–0,01                        |
| Depth of cut ( $a_p$ )<br>mm<br>inch        | 2–4<br>0,08–0,16                   | 0,5–2<br>0,02–0,08                    | 0,5–3<br>0,02–0,12                            |
| Carbide designation<br>ISO<br>US            | P20–P30<br>C6–C5<br>Coated carbide | P10<br>C7<br>Coated carbide or cermet | –   |

**MILLING****Face and square shoulder milling**

| Cutting data parameters                    | Milling with carbide               |  |
|--|------------------------------------|--|
|  | Rough milling                      | Fine milling                                 |
| Cutting speed ( $v_c$ )<br>m/min<br>f.p.m. | 110–160<br>360–525                 | 160–200<br>525–656                           |
| Feed ( $f_z$ )<br>mm/tooth<br>inch/tooth   | 0,2–0,4<br>0,008–0,016             | 0,1–0,2<br>0,004–0,008                       |
| Depth of cut ( $a_p$ )<br>mm<br>inch       | 2–5<br>0,08–0,2                    | ≤2<br>≤0,08                                  |
| Carbide designation<br>ISO<br>US           | P20–P40<br>C6–C5<br>Coated carbide | P10–P20<br>C6–C7<br>Coated carbide or cermet |

## End milling

| Cutting data parameters              | Type of milling  |  |   |
|--------------------------------------|--|--|---|
|                                      | Solid carbide  | Carbide indexable insert                             | High speed steel                                      |
| Cutting speed ( $v_c$ ) m/min f.p.m. | 70–100<br>230–328                                      | 100–140<br>328–460                                   | 30–35 <sup>1)</sup><br>98–115 <sup>1)</sup>           |
| Feed ( $f_z$ ) mm/tooth inch/tooth   | 0,006–0,20 <sup>2)</sup><br>0,0002–0,008 <sup>2)</sup> | 0,06–0,20 <sup>2)</sup><br>0,002–0,008 <sup>2)</sup> | 0,01–0,35 <sup>2)</sup><br>0,0004–0,014 <sup>2)</sup> |
| Carbide designation ISO US           | –  | P15–P40<br>C6–C5                                     | –   |

<sup>1)</sup> For coated HSS end mill  $v_c = 50–55$  m/min. (164–180 f.p.m.)

<sup>2)</sup> Depending on radial depth of cut and cutter diameter

## DRILLING

### High speed steel twist drill

| Drill diameter<br>inch | mm    | Cutting speed ( $v_c$ )<br>f.p.m. |        | Feed ( $f$ )<br>i.p.r.<br>mm/r |           |
|------------------------|-------|-----------------------------------|--------|--------------------------------|-----------|
|                        |       | m/min                             | i.p.r. | 0,002–0,004                    | 0,05–0,10 |
| –3/16                  | ≤5    | 46–52*                            | 14–16* | 0,002–0,004                    | 0,05–0,10 |
| 3/16–3/8               | 5–10  | 46–52*                            | 14–16* | 0,004–0,008                    | 0,10–0,20 |
| 3/8–5/8                | 10–15 | 46–52*                            | 14–16* | 0,008–0,010                    | 0,20–0,25 |
| 5/8–3/4                | 15–20 | 46–52*                            | 14–16* | 0,010–0,012                    | 0,25–0,30 |

\* For coated HSS drill  $v_c = 24–26$  m/min. (79–85 f.p.m.)

### Carbide drill

| Cutting data parameters              | Type of drill  |   |   |
|--------------------------------------|--|---|---|
|                                      | Indexable insert                                     | Solid carbide                                       | Brazed carbide <sup>1)</sup>                        |
| Cutting speed ( $v_c$ ) m/min f.p.m. | 180–200<br>590–656                                   | 90–110<br>295–360                                   | 60–90<br>197–295                                    |
| Feed ( $f$ ) mm/r i.p.r.             | 0,05–0,15 <sup>2)</sup><br>0,002–0,006 <sup>2)</sup> | 0,10–0,25 <sup>2)</sup><br>0,004–0,01 <sup>2)</sup> | 0,15–0,25 <sup>2)</sup><br>0,006–0,01 <sup>2)</sup> |

<sup>1)</sup> Drill with internal cooling channels and brazed tip

<sup>2)</sup> Depending on drill diameter



## GRINDING

A general grinding wheel recommendation is given below. More information can be found in the Uddeholm publication "Grinding of Tool Steel".

| Type of grinding             | Wheel recommendation |
|------------------------------|----------------------|
| Face grinding straight wheel | A 46 HV              |
| Face grinding segments       | A 36 GV              |
| Cylindrical grinding         | A 60 KV              |
| Internal grinding            | A 60 JV              |
| Profile grinding             | A 120 LV             |

## Welding

Good results when welding tool steel can be achieved if proper precautions are taken during welding (elevated working temperature, joint preparation, choice of consumables and welding procedure).

| Welding method  | TIG (GTAW)            |                                       | MMA (SMAW)                            |
|---|-----------------------|---------------------------------------|---------------------------------------|
| Working temperature   | 200–250°C (390–480°F) |                                       | 200–250°C (390–480°F)                 |
| Welding consumables   | STAVAX TIG-WELD       | Austenitic stainless steel Type ER312 | Austenitic stainless steel Type ER312 |
| Hardness after welding  | 54–56 HRC             | 28–30 HRC                             | 28–30 HRC                             |
| Hardness after tempering 2 x 2h at 530°C (990°F) 1 x 2h at 600°C (1220°F) | 50–52 HRC             | 28–30 HRC                             | 28–30 HRC                             |
|   | 41–43 HRC             | –                                     | –                                     |

A tempering temperature higher than 530°C (990°F) causes a reduction of the base material hardness. Tempering at 600°C (1220°F) reduce the hardness of the base material with 2–3 HRC

Ramax 2 has a high sulphur content, which means an increased risk for hot cracking during welding. To minimize the risk, keep the dilution as low as possible.

Further information is given in the Uddeholm brochure "Welding of Tool Steel".

## Further information

Please contact your local Uddeholm office for further information on the selection, heat treatment and application of Uddeholm tool steels, including the publication "Steels for Moulds".

## UDDEHOLM EUROPE

### AUSTRIA

UDDEHOLM  
Hansaallee 321  
D-40549 Düsseldorf  
Telephone: +49 211 535 10  
Telefax: +49 211 535 12 80

### BELGIUM

UDDEHOLM N.V.  
Waterstraat 4  
B-9160 Lokeren  
Telephone: +32 9 349 11 00  
Telefax: +32 9 349 11 11

### CROATIA

BOHLER UDDEHOLM Zagreb  
d.o.o za trgovinu  
Zitnjak b.b  
10000 Zagreb  
Telephone: +385 1 2459 301  
Telefax: +385 1 2406 790

### CZECHIA

BOHLER UDDEHOLM CZ s.r.o.  
Division Uddeholm  
U silnice 949  
161 00 Praha 6 Ruzyně  
Czech Republic  
Telephone: +420 233 029 850,8  
Telefax: +420 233 029 859

### DENMARK

UDDEHOLM A/S  
Kokmose 8, Bramdrupdam  
DK-6000 Kolding  
Telephone: +45 75 51 70 66  
Telefax: +45 75 51 70 44

### ESTONIA

UDDEHOLM TOOLING AB  
Silikatsiidi 7  
EE-0012 Tallinn  
Telephone: +372 655 9180  
Telefax: +372 655 9181

### FINLAND

OY UDDEHOLM AB  
Ritakuja 1, PL 57,  
FIN-01741 VANTAA  
Telephone: +358 9 290 490  
Telefax: +358 9 2904 9249

### FRANCE

UDDEHOLM S.A.  
12 Rue Mercier, Z.I. de Mitry-Compans  
F-77297 Mitry Mory Cedex  
Telephone: +33 (0)1 60 93 80 10  
Telefax: +33 (0)1 60 93 80 01

#### Branch office

UDDEHOLM S.A.  
77bis, rue de Vesoul  
La Nef aux Métiers  
F-25000 Besançon  
Telephone: +33 381 53 12 19  
Telefax: +33 381 53 13 20

### GERMANY

UDDEHOLM  
Hansaallee 321  
D-40549 Düsseldorf  
Telephone: +49 211 535 10  
Telefax: +49 211 535 12 80

#### Branch offices

UDDEHOLM  
Falkenstraße 21  
D-65812 Bad Soden/TS.  
Telephone: +49 6196 659 60  
Telefax: +49 6196 659 625

### UDDEHOLM

Albstraße 10  
D-73765 Neuhausen  
Telephone: +49 715 898 65-0  
Telefax: +49 715 898 65-25

### GREAT BRITAIN, IRELAND

UDDEHOLM UK LIMITED  
European Business Park  
Taylors Lane, Oldbury  
West Midlands B69 2BN  
Telephone: +44 121 552 55 11  
Telefax: +44 121 544 29 11  
Dublin Telephone: +353 1 45 14 01

## GREECE

UDDEHOLM STEEL TRADING COMPANY  
20, Athinon Street  
G-Piraeus 18540  
Telephone: +30 2 10 41 72 109/41 29 820  
Telefax: +30 2 10 41 72 767

### SKLERO S.A.

Steel Trading Comp. and  
Hardening Shop  
Frixou 11/Nikif. Ouranou  
G-54627 Thessaloniki  
Telephone: +30 31 51 46 77  
Telefax +30 31 54 12 50

## HUNGARY

UDDEHOLM TOOLING/BOK  
Dunaharaszt, Jedlik Ányos út 25  
H-2331 Dunaharaszt 1.Pf. 110  
Telephone/Telefax: +36 24 492 690

## ITALY

UDDEHOLM Italia S.p.A.  
Via Palizzi, 90  
I-20157 Milano  
Telephone: +39 02 35 79 41  
Telefax: +39 02 390 024 82

## LATVIA

UDDEHOLM TOOLING AB  
Deglava street 50  
LV-1035 Riga  
Telephone: +371 7 701 983, -981, -982  
Telefax: +371 7 701 984

## LITHUANIA

UDDEHOLM TOOLING AB  
BE PLIENIAS IR METALAI  
T. Masiliūlio 18b

LT-3014 Kaunas  
Telephone: +370 37 370613, -669  
Telefax: +370 37 370300

## THE NETHERLANDS

UDDEHOLM B.V.  
Isolatorweg 30  
NL-1014 AS Amsterdam  
Telephone: +31 20 581 71 11  
Telefax: +31 20 684 86 13

## NORWAY

UDDEHOLM A/S  
Jernkroken 18  
Postboks 85, Kalbakken  
N-0902 Oslo  
Telephone: +47 22 91 80 00  
Telefax: +47 22 91 80 01

## POLAND

INTER STAL CENTRUM  
Sp. z o.o./Co. Ltd.  
ul. Kolejowa 291, Dziekanów Polski  
PL-05-092 Lomianki  
Telephone: +48 22 429 2260  
Telefax: +48 22 429 2266

## PORTUGAL

F RAMADA Aços e Industrias S.A.  
P.O. Box 10  
P-3881 Ovar Codex  
Telephone: +351 56 58 61 11  
Telefax: +351 56 58 60 24

## ROMANIA

BÖHLER Romania SRL  
Uddeholm Branch  
Str. Atomistilor Nr 14A  
077125 Magurele Jud Ilfov  
Telephone: +40 214 575007  
Telefax: +40 214 574212

## RUSSIA

UDDEHOLM TOOLING CIS  
25 A Bolshoy pr PS  
197198 St. Petersburg  
Telephone: +7 812 233 9683  
Telefax: +7 812 232 4679

## SLOVAKIA

UDDEHOLM Slovakia  
Nástrojové oceľe, s.r.o.  
KRÁCINY 2  
036 01 Martin  
Telephone: +421 842 4 300 823  
Telefax: +421 842 4 224 028

## SLOVENIA

UDDEHOLM Italia S.p.A.  
Via Palizzi, 90  
I-20157 Milano  
Telephone: +39 02 35 79 41  
Telefax: +39 02 390 024 82

## SPAIN

UDDEHOLM  
Guifré 690-692  
E-08918 Badalona, Barcelona  
Telephone: +34 93 460 1227  
Telefax: +34 93 460 0558

#### Branch office

UDDEHOLM  
Barrio San Martin de Arteaga, 132  
Pol.Ind. Torrelarragoiti  
E-48170 Zamudio  
(Bizkaia)  
Telephone: +34 94 452 13 03  
Telefax: +34 94 452 13 58

## SWEDEN

UDDEHOLM TOOLING  
SVENSKA AB  
Aminogatan 25  
SE-431 53 Mölndal  
Telephone: +46 31 67 98 50  
Telefax: +46 31 27 02 94

## SWITZERLAND

HERTSCH & CIE AG  
General Wille Strasse 19  
CH-8027 Zürich  
Telephone: +41 1 208 16 66  
Telefax: +41 1 201 46 15

## UDDEHOLM NORTH AMERICA

### USA

UDDEHOLM  
4902 Tollview Drive  
Rolling Meadows IL 60008  
Telephone: +1 847 577 22 20  
Telefax: +1 847 577 80 28

### UDDEHOLM

548 Clayton Ct.,  
Wood Dale IL 60191  
Telephone: +1 630 350 10 00  
Telefax: +1 630 350 08 80

### UDDEHOLM

9331 Santa Fe Springs Road  
Santa Fe Springs, CA 90670  
Telephone: +1 562 946 65 03  
Telefax: +1 562 946 77 21

### UDDEHOLM

220 Cherry Street  
Shrewsbury, MA 01545  
Telephone: +1 508 845 1066  
Telefax: +1 508 845 3471

### CANADA

UDDEHOLM LIMITED  
2595 Meadowvale Blvd.  
Mississauga, Ontario L5N 7Y3  
Telephone: +1 905 812 9440  
Telefax: +1 905 812 8659

### MEXICO

ACEROS BOHLER UDDEHOLM,  
S.A. de C.V.  
Calle 8 No 2, Letra "C"  
Fraccionamiento Industrial Alce Blanco  
C.P. 52787 Naucalpan de Juarez  
Estado de Mexico  
Telephone: +52 55 9172 0242  
Telefax: +52 55 5576 6837

### UDDEHOLM

Lerdo de Tejada No.542  
Colonia Las Villas  
66420 San Nicolas de Los Garza, N.L.  
Telephone: +52 8-352 5239  
Telefax: +52 8-352 5356

## UDDEHOLM SOUTH AMERICA

### ARGENTINA

UDDEHOLM S.A.  
Mozart 40  
1619-Centro Industrial Garin  
Garin-Prov. Buenos Aires  
Telephone: +54 332 744 4440  
Telefax: +54 332 745 3222

### BRAZIL

UDDEHOLM ACOS ESPECIAIS Ltda.  
Estrada Yae Massumoto, 353  
CEP 09842-160  
Sao Bernardo do Campo - SP Brazil  
Telephone: +55 11 4393 4560, -4554  
Telefax: +55 11 4393 4561

## UDDEHOLM SOUTH AFRICA

UDDEHOLM Africa (Pty) Ltd.  
P.O. Box 539  
ZA-1600 Isando/Johannesburg  
Telephone: +27 11-974 2781  
Telefax: +27 11-392 2486

## UDDEHOLM AUSTRALIA

BOHLER-UDDEHOLM Australia  
129-135 McCredie Road  
Guildford NSW 2161  
Private Bag 14  
Telephone: +61 2 9681 3100  
Telefax: +61 2 9632 6161

#### Branch offices

Sydney, Melbourne, Adelaide,  
Brisbane, Perth, Newcastle,  
Launceston, Albury, Townsville

### ASSAB

ASSAB INTERNATIONAL  
Skytteholmsvägen 2  
P O Box 42  
SE-171 11 Solna  
Sweden  
Telephone: +46 8 564 616 70  
Telefax: +46 8 25 02 37

#### Subsidiaries

India, Iran, Turkey, United Arab  
Emirates

#### Distributors in

Africa, Latin America, Middle East  
  
ASSAB PACIFIC  
ASSAB Pacific Pte. Ltd  
171, Chin Swee Road  
No. 07-02, San Centre  
Singapore 169877  
Telephone: +65 534 56 00  
Telefax: +65 534 06 55  
  
Subsidiaries  
China, Hong Kong, Indonesia, Japan,  
Korea, Malaysia, Philippine Islands,  
Singapore, Taiwan, Thailand

When the first idea pops into your head, throughout the development process to the release of the new product, we'll be your partner. As the world's leading supplier of tooling materials and related services, we can be trusted. Meet us under the Uddeholm and ASSAB brands, wherever in the world you have your business.

