


4140 High tensile

Typical Analysis (Ave. values %)	C	Si	Mn	Ni	Cr	Mo	S	P	
	0.4	0.2	0.8	-	1.0	0.2	0.025	0.025	
NEAREST STANDARD	AS		DIN		BS		AISI		
	4140		1.7225 41CrMo4		EN19A		4140		

DESCRIPTION	Chromium, Molybdenum steel for applications requiring high tensile strength and toughness values, in particular in medium and large cross sections in the quenched and tempered condition. The Molybdenum additions prevent the steel from being susceptible to temper brittleness. Surface hardenable
--------------------	--

APPLICATIONS	4140 is the most commonly used of the high tensile steels with a wide range of applications in automotive, Gear and Engine construction, Crankshafts, Steering knuckles, Connecting rods, Spindles, Intermediate gears, Pump and Gear shafts, Axles, Nuts and Bolts.
---------------------	--

HEAT TREATMENT	Forge	850-1050°C. Cool in furnace.
	Normalize	840-880°C. Air cool.
	Anneal	680-720°C. Cool slowly in controlled furnace.
	Stress relieve	In the quenched and tempered condition, about 30-50°C below the tempering temperature. Air cool. In the annealed condition, 600-650°C. Air cool.
	Harden	830-860°C Oil quench.
	Temper	540-680°C hold for 1 hour min. at temperature, air cool. (see tempering chart)
	Nitride	Suitable for both liquid and gas nitriding.

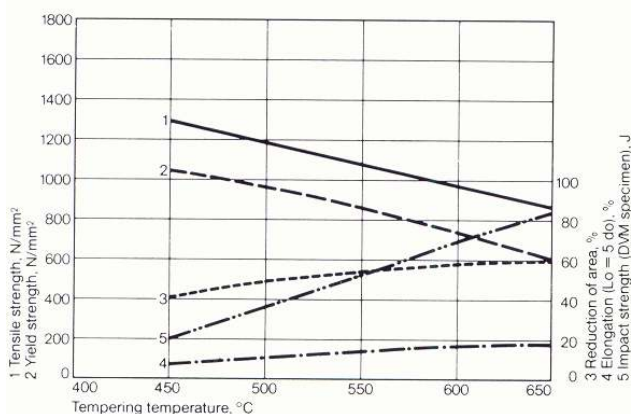

Hardening temperature: 840°C
Quenched and tempered
Specimen size: 60 mm diameter

WELDING	<p>Parts should be welded in the hardened and tempered condition. Strength properties of the joint will not be the same as the base metal. Preheat 300-400°C. Temper after welding to about 35-50°C below the recommended tempering temperature. Filler metal: - FOX CM2-KB electrodes or CM2-IGwire. For advice in connection with difficult welding, please consult our engineers.</p>
----------------	--

MECHANICAL PROPERTIES Heat Treated Condition	Condition	Ruling section mm	Tensile Strength MPa	Yield Strength MPa	Elong. %	Izod Impact J	Brinell Hardness
	R	250	780-850	480	15	34	201-255
	S	250	770-930	540	13	27	223-277
	S	150	770-930	570	15	54	223-277
	T	100	850-1000	665	13	54	248-302
	U	63	930-1080	740	12	47	269-331
	V	30	1000-1150	835	12	47	293-352
	W	20	1080-1230	925	12	40	311-375

HIGH TEMPERATURE STRENGTH	For quenched and tempered heavy forgings.								
	Diameter		Yield strength MPa						
	Over	Up to	20°C	100°C	200°C	250°C	300°C	350°C	400°C
		250	510	486	461	441	422	392	363
	250	500	460	431	412	402	382	353	324
500	750	390	333	333	324	304	275	245	

PHYSICAL PROPERTIES	Density (kg/dm ³)	7.85				
	Modulus of elasticity 10 ³ N/mm ²	210				
	Thermal conductivity W/(m.K)	42				
	Electric resistivity Ohm.mm ² /m	0.19				
	Specific heat capacity J/(kg.K)	460				
	Modulus of elasticity 10 ³ N/mm ²	100°C	200°C	300°C	400°C	500°C
		205	195	185	175	165
Thermal expansion 10 ⁶ m/(m.K)	100°C	200°C	300°C	400°C	500°C	
	11.1	12.1	12.9	13.5	13.9	

SIZE RANGE	Round	10 to 650 mm
	Hollow	45/28 to 200/140 mm
	Hexagon	19 to 75 mm A/F
	Square	28 to 127 mm
	Flat	76.2 x 38.1 mm
	Chrome Bar	19.05 to 101.6 mm Dia.
	Ground	12.7 to 110 mm Dia. (H9 Tolerance)
	Peeled & polished	19.05 to 101.6 mm Dia. (H11 Tolerance)

LOCATIONS				
Bohler Uddeholm Australia Pty Ltd ABN 15000013052				
Sydney	129-135 McCredie Rd Guildford	2161	Ph (02) 8724 5554	Fax (02) 8724 5555
Newcastle	3 Pavilion Pl Cardiff	2285	Ph (02) 4954 6611	Fax (02) 4956 5773
Albury	1 Eames St Albury	2640	Ph (02) 6041 3399	Fax (02) 6041 1820
Wollongong	40 Doyle Ave Unanderra	2526	Ph (02) 4272 6544	Fax (02) 4272 7563
Marayong	1/21 Binney Rd Marayong	2148	Ph (02) 9831 4431	Fax (02) 9671 1682
Melbourne	282-290 Greens Rd Dandenong	3175	Ph (03) 9767 5554	Fax (03) 9767 5555
Bayswater	4 Amsted Rd Bayswater	3153	Ph (03) 9739 8022	Fax (03) 9739 8033
Adelaide	1 Williams Cir Pooraka	5095	Ph (08) 8368 4554	Fax (08) 8368 4555
Brisbane	12-18 Limestone St Darra	4076	Ph (07) 3712 9554	Fax (07) 3712 9555
Townsville	9-11 Caldwell St Garbutt	4814	Ph (07) 4479 4800	Fax (07) 4725 1316
Perth	29-33 Gauge Cir Canningvale	6155	Ph (08) 9455 8672	Fax (08) 9455 8673
Kewdale	5 Beete St Welshpool	6106	Ph (08) 9350 9582	Fax (08) 9350 9683
Launceston	20 Murphy St Invermay	7248	Ph (03) 6334 3542	Fax (03) 6331 4001
www.buau.com.au				
Every care has been taken in listing this information, particularly specifications. Bohler Uddeholm Australia Pty Ltd will not accept responsibility for any loss or other damage caused to any person or Company as a result of the use of information contained herein				

Notes