

ORVAR[®] 2 Microdized

Hot work tool steel

COLD WORK

PLASTIC MOULDING

HOT WORK

HIGH PERFORMANCE STEEL




This information is based on our present state of knowledge and is intended to provide general notes on our products and their uses. It should not therefore be construed as a warranty of specific properties of the products described or a warranty for fitness for a particular purpose.

General

Orvar 2 Microdized is a chromium-molybdenum-vanadium-alloyed steel which is characterized by:

- Good resistance to abrasion at both low and high temperatures
- High level of toughness and ductility
- Uniform and high level of machinability and polishability
- Good high-temperature strength and resistance to thermal fatigue
- Excellent through-hardening properties
- Very limited distortion during hardening.

| | | | | | | |
|------------------------|---|-----------|-----------|-----------|-----------|----------|
| Typical analysis % | C 0,39 | Si 1,0 | Mn 0,4 | Cr 5,3 | Mo 1,3 | V 0,9 |
| Standard specification | AISI H13, W.-Nr. 1.2344, EN X40CrMoV5-1 | | | | | |
| Delivery condition | Soft annealed to approx. 185 HB | | | | | |
| Colour code | Orange/violet | | | | | |

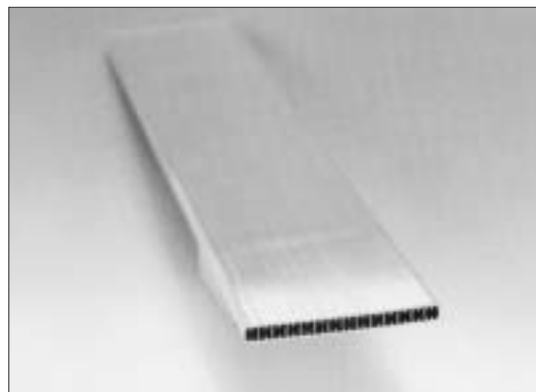

Applications

TOOLS FOR EXTRUSION

| Part | Aluminium, magnesium alloys, HRC | Copper alloys HRC | Stainless steel HRC |
|---|----------------------------------|---------------------------|---------------------|
| Dies Backers, die-holders, liners, dummy blocks, stems | 44–50 41–50 | 43–47 40–48 | 45–50 40–48 |
| Austenitizing temperature (approx.) | 1020–1030°C (1870–1885°F) | 1040–1050°C (1900–1920°F) | |

PLASTIC MOULDING APPLICATIONS

| Part | Austenitizing temp. | HRC |
|---|--|-------|
| Injection moulds Compression/ transfer moulds | 1020–1030°C (1870–1885°F) Tempering 250°C (480°F) | 50–52 |

OTHER APPLICATIONS

| Application | Austenitizing temp. | HRC |
|---|---|--|
| Severe cold punching, scrap shears | 1020–1030°C (1870–1885°F) Tempering 250°C (480°F) | 50–52 |
| Hot shearing | 1020–1030°C (1870–1885°F) Tempering 250°C (480°F) or 575–600°C (1070–1110°F) | 50–52 45–50 |
| Shrink rings (e.g. for cemented carbide dies) | 1020–1030°C (1870–1885°F) Tempering 575–600°C (1070–1110°F) | 45–50 |
| Wear-resisting parts | 1020–1030°C (1870–1885°F) Tempering 575°C (1070°F) Nitriding | Core 50–52 Surface ~1000HV ₁ |

For applications requiring extreme levels of toughness and ductility e.g. die-casting dies, forging dies, the premium-grade H13-steel, Orvar Supreme, is recommended.

Properties

PHYSICAL DATA

Unless otherwise is indicated all specimens were hardened 30 minutes at 1025°C (1875°F), quenched in air and tempered 2 + 2 h at 610°C (1130°F). The hardness were 45 ± 1 HRC.


| Temperature | 20°C (68°F) | 400°C (750°F) | 600°C (1110°F) |
|--|-----------------------------------|---|---|
| Density kg/m ³ lbs/in ³ | 7800 0,281 | 7700 0,277 | 7600 0,274 |
| Modulus of elasticity N/mm ² psi | 210 000 30,5 x 10 ⁶ | 180 000 26,1 x 10 ⁶ | 140 000 20,3 x 10 ⁶ |
| Coefficient of thermal expansion per °C from 20°C per °F from 68°F | – – | 12,6 x 10 ⁻⁶ 7,0 x 10 ⁻⁶ | 13,2 x 10 ⁻⁶ 7,3 x 10 ⁻⁶ |
| Thermal conductivity W/m °C Btu in/(ft ² h°F) | 25 176 | 29 204 | 30 211 |

MECHANICAL PROPERTIES

Approximate tensile strength at room temperature.

| Hardness | 52 HRC | 45 HRC |
|--|-------------------------------|------------------------------|
| Tensile strength Rm N/mm ² kp/mm ² tsi psi | 1820 185 117 263 000 | 1420 145 92 206 000 |
| Yield point Rp0,2 N/mm ² kp/mm ² tsi psi | 1520 155 98 220 000 | 1280 130 83 185 000 |

Approximate strength at elevated temperatures
Longitudinal direction.

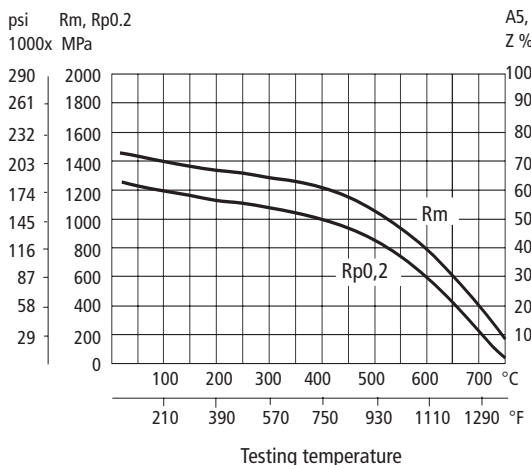

Heat treatment

SOFT ANNEALING

Protect the steel and heat through to 850°C (1560°F). Then cool in the furnace at 10°C (20°F) per hour to 650°C (1200°F), then freely in air.

STRESS RELIEVING

After rough machining the tool should be heated through to 650°C (1200°F), holding time 2 hours. Cool slowly to 500°C (930°F), then freely in air.

HARDENING

Pre-heating temperature: 600–850°C (1110–1560°F), normally in two pre-heating steps.

Austenitizing temperature: 1020–1050°C (1870–1920°F), normally 1020–1030°C (1870–1885°F).

| Temperature | | Soaking* time minutes | Hardness before tempering |
|-------------|------|--------------------------|------------------------------|
| °C | °F | | |
| 1025 | 1875 | 30 | 53±2 HRC |
| 1050 | 1920 | 15 | 54±2 HRC |


* Soaking time = time at hardening temperature after the tool is fully heated through.

Protect the part against decarburization and oxidation during hardening.



CCT graph

Austenitizing temperature 1020°C (1870°F). Holding time 30 minutes.

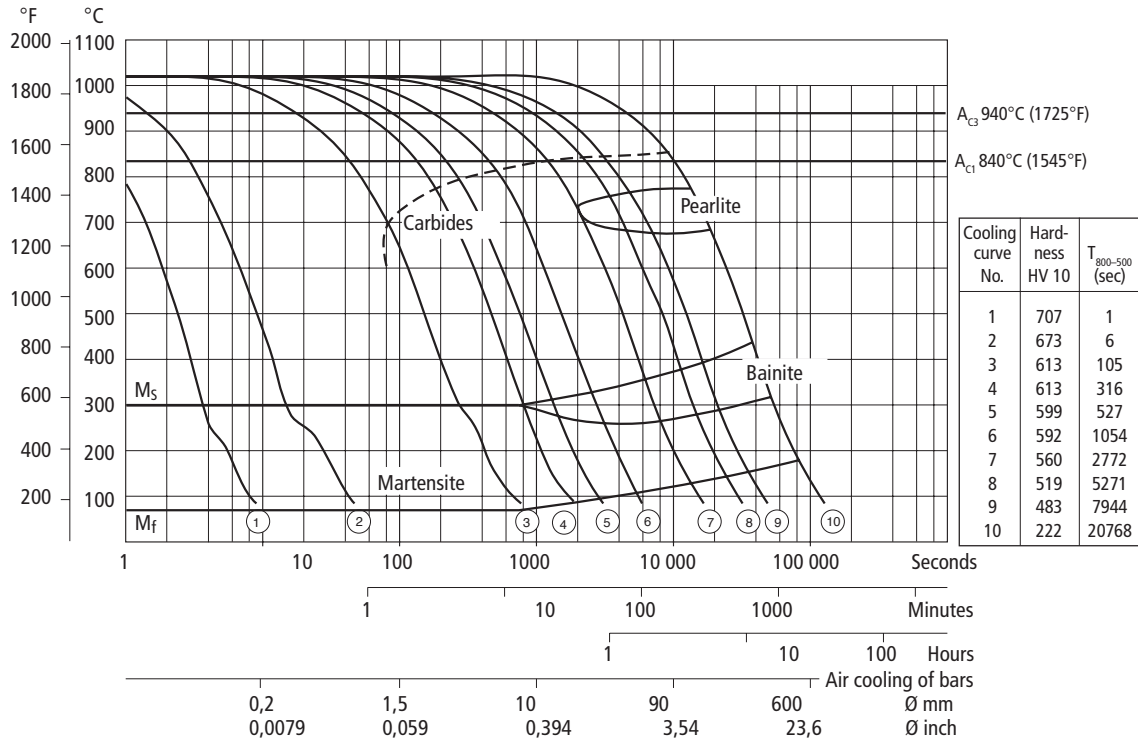


QUENCHING MEDIA

- High speed gas/circulating atmosphere
- Vacuum (high speed gas with sufficient positive pressure). An interrupted quench is recommended where distortion control and quench cracking are a concern
- Martempering bath or fluidized bed at 450–550°C (840–1020°F), then cool in air
- Martempering bath or fluidized bed at approx. 180–220°C (360–430°F) then cool in air
- Warm oil.

Note 1: Temper the tool as soon as its temperature reaches 50–70°C (120–160°F).

Note 2: In order to obtain the optimum properties for the tool, the cooling rate should be fast, but not at a level that gives excessive distortion or cracks.


Hardness, grain size and retained austenite as functions of austenitizing temperature

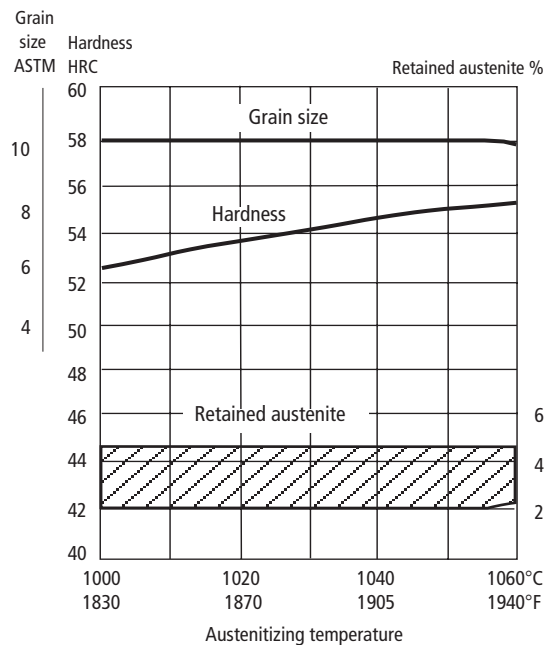

TEMPERING


Choose the tempering temperature according to the hardness required by reference to the tempering graph. Temper twice with intermediate cooling to room temperature. Lowest tempering temperature 180°C (360°F). Holding time at temperature minimum 2 hours. Do not temper in the range 425–550°C (800–1020°F).

Tempering graph

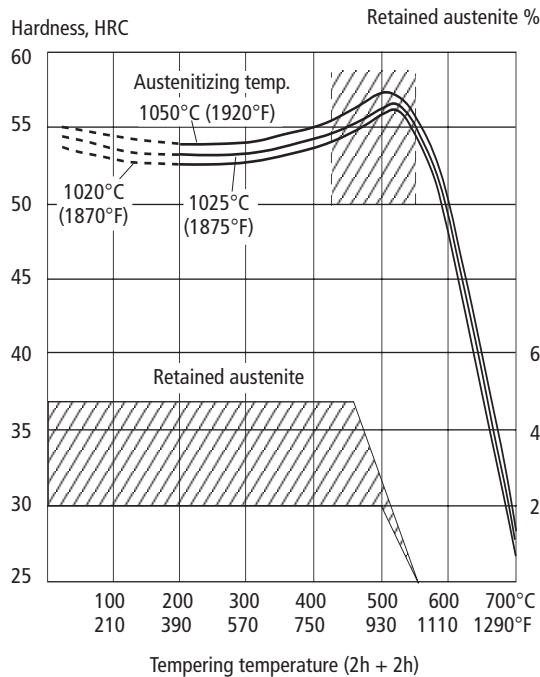

Tempering within the range 425–550°C (800–1020°F) is not normally recommended due to the reduction in toughness properties.

Effect of time at tempering temperature

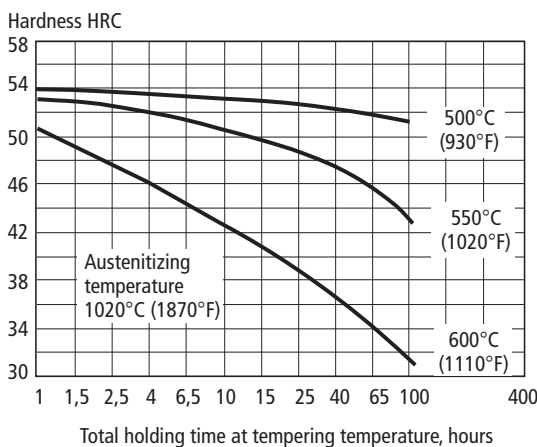


DIMENSIONAL CHANGES DURING HARDENING

Sample plate, 100 x 100 x 25 mm, 4" x 4" x 1".

| | | Width % | Length % | Thickness % |
|-----------------------------------|------|---------|----------|-------------|
| Oil hardened from 1020°C (1870°F) | Min. | -0,08 | -0,06 | ±0 |
| | Max. | -0,15 | -0,16 | +0,30 |
| Air hardened from 1020°C (1870°F) | Min. | -0,02 | -0,05 | ±0 |
| | Max. | +0,03 | +0,02 | +0,05 |
| Vac hardened from 1020°C (1870°F) | Min. | +0,01 | -0,02 | +0,08 |
| | Max. | +0,02 | -0,04 | +0,12 |

DIMENSIONAL CHANGES DURING TEMPERING

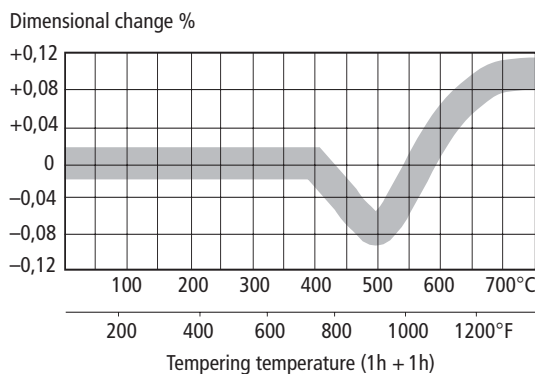

Note: The dimensional changes in hardening and tempering should be added.

NITRIDING AND NITROCARBURIZING

Nitriding and nitrocarburizing result in a hard surface layer which is very resistant to wear and erosion. The nitrided layer is, however, brittle and may crack or spall when exposed to mechanical or thermal shock, the risk increasing with layer thickness. Before nitriding, the tool should be hardened and tempered at a temperature at least 25–50°C (45–90°F) above the nitriding temperature.

Nitriding in ammonia gas at 510°C (950°F) or plasma nitriding in a 75% hydrogen/25% nitrogen mixture at 480°C (895°F) both result in a surface hardness of about 1100 HV_{0,2}. In general, plasma nitriding is the preferred method because of better control over nitrogen potential; in particular, formation of the so-called white layer, which is not recommended for hot-work service, can readily be avoided. However, careful gas nitriding can give perfectly acceptable results.

Orvar 2 Microdized can also be nitrocarburized in either gas or salt bath. The surface hardness after nitrocarburizing is 900–1000 HV_{0,2}.

DEPTH OF NITRIDING

| Process | Time | Depth | |
|---|--------------|--------------|------------------|
| | | mm | inch |
| Gas nitriding at 510°C (950°F) | 10 h 30 h | 0,12 0,20 | 0,0047 0,0079 |
| Plasma nitriding at 480°C (895°F) | 10 h 30 h | 0,12 0,18 | 0,0047 0,0071 |
| Nitrocarburizing – in gas at 580°C (1075°F) | 2,5 h | 0,11 | 0,0043 |
| – in salt bath at 580°C (1075°F) | 1 h | 0,06 | 0,0024 |

Nitriding to case depths >0,3 mm (0,012 inch) is not recommended for hot-work applications.

Orvar 2 Microdized can be nitrided in the soft-annealed condition. The hardness and depth of case will, however, be reduced somewhat in this case.

Machining recommendations

The cutting data below are to be considered as guiding values, which must be adapted to existing local conditions.

More information can be found in the Uddeholm publication "Cutting data recommendations".

Condition: Sof annealed to approx. 185 HB

TURNING

| Cutting data parameters | Turning with carbide | | Turning with high speed steel Fine turning |
|--|------------------------------------|---------------------------------------|---|
| | Rough turning | Fine turning | |
| Cutting speed (v_c) m/min f.p.m. | 200–250 656–820 | 250–300 820–984 | 25–30 82–98 |
| Feed (f) mm/r i.p.r. | 0,2–0,4 0,008–0,016 | 0,05–0,2 0,002–0,008 | 0,05–0,3 0,002–0,01 |
| Depth of cut (a_p) mm inch | 2–4 0,08–0,16 | 0,5–2 0,02–0,08 | 0,5–3 0,02–0,12 |
| Carbide designation ISO US | P20–P30 C6–C5 Coated carbide | P10 C7 Coated carbide or cermet | – – |

DRILLING**High speed steel twist drill**

| Drill diameter | | Cutting speed, v_c | | Feed, f | |
|----------------|----------|----------------------|--------|-----------|-------------|
| mm | inch | m/min | f.p.m. | mm/r | i.p.r. |
| – 5 | –3/16 | 16–18* | 52–59* | 0,05–0,15 | 0,002–0,006 |
| 5–10 | 3/16–3/8 | 16–18* | 52–59* | 0,15–0,20 | 0,006–0,008 |
| 10–15 | 3/8–5/8 | 16–18* | 52–59* | 0,20–0,25 | 0,008–0,010 |
| 15–20 | 5/8–3/4 | 16–18* | 52–59* | 0,25–0,35 | 0,010–0,014 |

* For coated HSS drill $v_c = 28–30$ m/min. (92–98 f.p.m.).

Carbide drill

| Cutting data parameters | Type of drill | | |
|--|--|--|--|
| | Indexable insert | Solid carbide | Brazed carbide ¹⁾ |
| Cutting speed (v_c) m/min f.p.m. | 220–240 720–785 | 130–160 425–525 | 80–110 260–360 |
| Feed (f) mm/r i.p.r. | 0,03–0,10 ²⁾ 0,001–0,004 ²⁾ | 0,10–0,25 ²⁾ 0,004–0,010 ²⁾ | 0,15–0,25 ²⁾ 0,006–0,010 ²⁾ |

¹⁾ Drill with internal cooling channels and brazed carbide tip.

²⁾ Depending on drill diameter.

MILLING**Face and square shoulder milling**

| Cutting data parameters | Milling with carbide | |
|--|------------------------------------|--|
| | Rough milling | Fine milling |
| Cutting speed (v_c) m/min f.p.m. | 180–260 591–853 | 260–300 853–984 |
| Feed (f_z) mm/tooth inch/tooth | 0,2–0,4 0,008–0,016 | 0,1–0,2 0,004–0,008 |
| Depth of cut (a_p) mm inch | 2–5 0,08–0,2 | –2 –0,08 |
| Carbide designation ISO US | P20–P40 C6–C5 Coated carbide | P10–P20 C6–C7 Coated carbide or cermet |

End milling

| Cutting data parameters | Type of end mill | | |
|--|--|--|--|
| | Solid carbide | Carbide indexable insert | High speed steel |
| Cutting speed (v_c) m/min f.p.m. | 160–200 525–660 | 170–230 560–755 | 35–40 ¹⁾ 115–130 ¹⁾ |
| Feed (f_z) mm/tooth inch/tooth | 0,03–0,20 ²⁾ 0,001–0,008 ²⁾ | 0,08–0,20 ²⁾ 0,003–0,008 ²⁾ | 0,05–0,35 ²⁾ 0,002–0,014 ²⁾ |
| Carbide designation ISO | – | P20, P30 | – |

¹⁾ For coated HSS end mill $v_c = 55–60$ m/min. (180–195 f.p.m.).

²⁾ Depending on radial depth of cut and cutter diameter.

GRINDING

A general grinding wheel recommendation is given below. More information can be found in the Uddeholm brochure "Grinding of Tool Steel" and can also be obtained from the grinding wheel manufacturer.

Wheel recommendation

| Type of grinding | Soft annealed condition | Hardened condition |
|------------------------------|-------------------------|--------------------|
| Face grinding straight wheel | A 46 HV | A 46 HV |
| Face grinding segments | A 24 GV | A 36 GV |
| Cylindrical grinding | A 46 LV | A 60 KV |
| Internal grinding | A 46 JV | A 60 IV |
| Profile grinding | A 100 LV | A 120 KV |

Electrical-discharge machining

If spark-erosion is performed in the hardened and tempered condition, the white re-cast layer should be removed mechanically e.g. by grinding or stoning. The tool should then be given an additional temper at approx. 25°C (50°F) below the previous tempering temperature.

Welding

Welding of tool steel can be performed with good results if proper precautions are taken regarding elevated temperature, joint preparation, choice of consumables and welding procedure.

| Welding method | TIG | MMA |
|-------------------------------------|--|------------------------|
| Working temperature | 325–375°C 620–710°F | 325–375°C 620–710°F |
| Filler metal | QRO 90 TIG-WELD DIEVAR TIG-WELD | QRO 90 WELD |
| Cooling rate | 20–40°C/h (35–70°F/h) the first 2–3 h then freely in air. | |
| Hardness after welding | 50–55 HRC | 50–55 HRC |
| Heat treatment after welding | | |
| Hardened condition | Temper at 25°C (45°F) below the original tempering temperature. | |
| Soft annealed condition | Soft-anneal the material at 850°C (1560°F) in protected atmosphere. Then cool in the furnace at 10°C (20°F) per hour to 650°C (1200°F) then freely in air. | |

More detailed information can be found in the Uddeholm brochure "Welding of Tool Steel".

Hard-chromium plating

After plating, parts should be tempered at 180°C (360°F) for 4 hours within 4 hours of plating to avoid the risk of hydrogen embrittlement.

Photo-etching

Orvar 2 Microdized is particularly suitable for texturing by the photo-etching method. Its high level of homogeneity and low sulphur content ensures accurate and consistent pattern reproduction.

Polishing

Orvar 2 Microdized exhibits good polishability in the hardened and tempered condition. Polishing after grinding can be effected using aluminium oxide or diamond paste.

Typical procedure:

1. Rough grinding to 180–320 grain size using a wheel or stone.
2. Fine grinding with abrasive paper or powder down to 400–800 grain size.
3. Polish with diamond paste grade 15 (15µm grain size) using a polishing tool of soft wood or fibre.
4. Polish with diamond paste 8–6–3 (8–6–3µm grain size) using a polishing tool of soft wood or fibre.
5. When demands on surface finish are high, grade 1 (1µm grain size) diamond paste can be used for final polishing with a fibre polishing pad.

Further information

Please contact your local Uddeholm office for further information on the selection, heat treatment, application and availability of Uddeholm tool steels.

UDDEHOLM EUROPE

AUSTRIA

UDDEHOLM
Hansaallee 321
D-40549 Düsseldorf
Telephone: +49 211 535 10
Telefax: +49 211 535 12 80

BELGIUM

UDDEHOLM N.V.
Waterstraat 4
B-9160 Lokeren
Telephone: +32 9 349 11 00
Telefax: +32 9 349 11 11

CROATIA

BOHLER UDDEHOLM Zagreb
d.o.o. za trgovinu
Zitnjak b.b
10000 Zagreb
Telephone: +385 1 2459 301
Telefax: +385 1 2406 790

CZECHIA

BOHLER UDDEHOLM CZ s.r.o.
Division Uddeholm
U silnice 949
161 00 Praha 6 Ruzyně
Czech Republic
Telephone: +420 233 029 850,8
Telefax: +420 233 029 859

DENMARK

UDDEHOLM A/S
Kokmose 8, Bramdrupdam
DK-6000 Kolding
Telephone: +45 75 51 70 66
Telefax: +45 75 51 70 44

ESTONIA

UDDEHOLM TOOLING ESTI OÜ
Siilikatsiidi 7
EE-11216 Tallinn
Telephone: +372 655 9180
Telefax: +372 655 9181

FINLAND

OY UDDEHOLM AB
Ritakuja 1, PL 57,
FIN-01741 VANTAA
Telephone: +358 9 290 490
Telefax: +358 9 2904 9249

FRANCE

UDDEHOLM S.A.
12 Rue Mercier, Z.I. de Mitry-Compans
F-77297 Mitry Mory Cedex
Telephone: +33 (0)1 60 93 80 10
Telefax: +33 (0)1 60 93 80 01

Branch office

UDDEHOLM S.A.
77bis, rue de Vesoul
La Nef aux Métiers
F-25000 Besançon
Telephone: +33 381 53 12 19
Telefax: +33 381 53 13 20

GERMANY

UDDEHOLM
Hansaallee 321
D-40549 Düsseldorf
Telephone: +49 211 535 10
Telefax: +49 211 535 12 80

Branch offices

UDDEHOLM
Falkenstraße 21
D-65812 Bad Soden/TS.
Telephone: +49 6196 659 60
Telefax: +49 6196 659 625

UDDEHOLM

Albstraße 10
D-73765 Neuhausen
Telephone: +49 715 898 65-0
Telefax: +49 715 898 65-25

GREAT BRITAIN, IRELAND

UDDEHOLM UK LIMITED
European Business Park
Taylors Lane, Oldbury
West Midlands B69 2BN
Telephone: +44 121 552 55 11
Telefax: +44 121 544 29 11

Dublin Telephone: +353 1 45 14 01

GREECE

UDDEHOLM STEEL TRADING
COMPANY
20, Athinon Street
G-Piraeus 18540
Telephone: +30 2 10 41 72 109/41 29 820
Telefax: +30 2 10 41 72 767

Agency

SKLERO S.A.
Steel Trading Comp. and
Hardening Shop
Frixou 11/Nikif. Ouranou
G-54627 Thessaloniki
Telephone: +30 31 51 46 77
Telefax +30 31 54 12 50
SKLERO S.A.
Heat Treatment and Trading of Steel
Uddeholm Tool Steels
Industrial Area of Thessaloniki
P.O. Box 1123
G-57022 Sindos, Thessaloniki
Telephone: +30 23 10 79 76 46
Telefax: +30 23 10 79 76 78

HUNGARY

UDDEHOLM TOOLING/BOK
Dunaharaszti, Jedlik Ányos út 25
H-2331 Dunaharaszti 1.Pf. 110
Telephone/Telefax: +36 24 492 690

ITALY

UDDEHOLM div. della Bohler
Uddeholm Italia S.p.A.
Via Palizzi, 90
I-20157 Milano
Telephone: +39 02 35 79 41
Telefax: +39 02 390 024 82

LATVIA

UDDEHOLM TOOLING AB
Piedrujas street 7
LV-1073 Riga
Telephone: +371 7 703 133
Telefax: +371 7 185 079

LITHUANIA

UDDEHOLM TOOLING AB
BE PLIENAS IR METALAI
T. Masiulio 18b
LT-52459 Kaunas
Telephone: +370 37 370613, -669
Telefax: +370 37 370300

THE NETHERLANDS

UDDEHOLM B.V.
Isolatorweg 30
NL-1014 AS Amsterdam
Telephone: +31 20 581 71 11
Telefax: +31 20 684 86 13

NORWAY

UDDEHOLM A/S
Jernkroken 18
Postboks 85, Kalbakken
N-0902 Oslo
Telephone: +47 22 91 80 00
Telefax: +47 22 91 80 01

POLAND

INTER STAL CENTRUM
Sp. z o.o./Co. Ltd.
ul. Kolejowa 291, Dziekanów Polski
PL-05-092 Lomianki
Telephone: +48 22 429 2260
Telefax: +48 22 429 2266

PORTUGAL

F RAMADA Aços e Industrias S.A.
P.O. Box 10
P-3881 Ovar Codex
Telephone: +351 56 58 61 11
Telefax: +351 56 58 60 24

ROMANIA

BÖHLER Romania SRL
Uddeholm Branch
Str. Atomistilor Nr 14A
077125 Magurele Jud Ilfov
Telephone: +40 214 575007
Telefax: +40 214 574212

RUSSIA

UDDEHOLM TOOLING CIS
25 A Bolshoy pr PS
197198 St. Petersburg
Telephone: +7 812 233 9683
Telefax: +7 812 232 4679

SLOVAKIA

UDDEHOLM Slovakia
Nástrojové ocele, s.r.o
KRÁČINY 2
036 01 Martin
Telephone: +421 842 4 300 823
Telefax: +421 842 4 224 028

SLOVENIA

UDDEHOLM div. della Bohler
Uddeholm Italia S.p.A.
Via Palizzi, 90
I-20157 Milano
Telephone: +39 02 35 79 41
Telefax: +39 02 390 024 82

SPAIN

UDDEHOLM
Guifré 690-692
E-08918 Badalona, Barcelona
Telephone: +34 93 460 1227
Telefax: +34 93 460 0558

Branch office

UDDEHOLM
Barrio San Martin de Arteaga, 132
Pol.Ind. Torrelarragoiti
E-48170 Zamudio
(Bizkaia)
Telephone: +34 94 452 13 03
Telefax: +34 94 452 13 58

SWEDEN

UDDEHOLM TOOLING
SVENSKA AB
Aminogatan 25
SE-431 53 Mölndal
Telephone: +46 31 67 98 50
Telefax: +46 31 27 02 94

SWITZERLAND

HERTSCH & CIE AG
General Wille Strasse 19
CH-8027 Zürich
Telephone: +41 44 208 16 66
Telefax: +41 44 201 46 15

UDDEHOLM NORTH AMERICA

USA

UDDEHOLM
4902 Tollview Drive
Rolling Meadows, IL 60008
Sales Phone: +1 800 638 2520
Sales Fax: +1 630 350 0880

Region East Warehouse
UDDEHOLM – Shrewsbury, MA

Region Central Warehouse
UDDEHOLM – Wood Dale, IL

Region West Warehouse
UDDEHOLM – Santa Fe Springs, CA

CANADA

UDDEHOLM
2595 Meadowvale Blvd.
Mississauga, ON L5N 7Y3
Telephone: +1 905 812 9440
Telefax: +1 905 812 8658

Branch Warehouses

UDDEHOLM – St. Laurent, QC
UDDEHOLM – New Westminster, BC

Heat Treating

THERMO-TECH – Mississauga, ON

MEXICO

ACEROS BOHLER UDDEHOLM,
S.A. de C.V.
Calle 8 No 2, Letra "C"
Fraccionamiento Industrial Alce Blanco
C.P. 52787 Naucalpan de Juarez
Estado de Mexico
Telephone: +52 55 9172 0242
Telefax: +52 55 5576 6837

UDDEHOLM

Letrado de Tejada No.542
Colonia Las Villas
66420 San Nicolas de Los Garza, N.L.
Telephone: +52 8-352 5239
Telefax: +52 8-352 5356

UDDEHOLM SOUTH AMERICA

ARGENTINA

UDDEHOLM S.A
Mozart 40
1619-Centro Industrial Garin
Garin-Prov. Buenos Aires
Telephone: +54 332 744 4440
Telefax: +54 332 745 3222

BRAZIL

UDDEHOLM ACOS ESPECIAIS Ltda.
Estrada Yae Massumoto, 353
CEP 09842-160
Sao Bernardo do Campo - SP Brazil
Telephone: +55 11 4393 4560, -4554
Telefax: +55 11 4393 4561

UDDEHOLM SOUTH AFRICA

UDDEHOLM Africa (Pty) Ltd.
P.O. Box 539
ZA-1600 Isando/Johannesburg
Telephone: +27 11-974 2781
Telefax: +27 11-392 2486

UDDEHOLM AUSTRALIA

BOHLER-UDDEHOLM Australia
129-135 McCredie Road
Guildford NSW 2161
Private Bag 14
Telephone: +61 2 9681 3100
Telefax: +61 2 9632 6161

Branch offices

Sydney, Melbourne, Adelaide,
Brisbane, Perth, Newcastle,
Launceston, Albury, Townsville

ASSAB

ASSAB INTERNATIONAL

Skytteholmsvägen 2
P O Box 42
SE-171 11 Solna
Sweden
Telephone: +46 8 564 616 70
Telefax: +46 8 25 02 37

Subsidiaries

India, Iran, Turkey, United Arab
Emirates, Saudi Arabia
Distributors in
Africa, Latin America, Middle East

ASSAB PACIFIC

ASSAB Pacific Pte. Ltd
171, Chin Swee Road
No. 07-02, San Centre
Singapore 169877
Telephone: +65 534 56 00
Telefax: +65 534 06 55

Subsidiaries

China, Hong Kong, Indonesia, Japan,
Korea, Malaysia, Philippine Islands,
Singapore, Taiwan, Thailand

When the first idea pops into your head, throughout the development process to the release of the new product, we'll be your partner. As the world's leading supplier of tooling materials and related services, we can be trusted. Meet us under the Uddeholm and ASSAB brands, wherever in the world you have your business.

