

VANADIS[®] 30 SuperClean³

Powder metallurgical cold work tool steel

COLD WORK

PLASTIC MOULDING

HOT WORK

HIGH PERFORMANCE STEEL



This information is based on our present state of knowledge and is intended to provide general notes on our products and their uses. It should not therefore be construed as a warranty of specific properties of the products described or a warranty for fitness for a particular purpose.

Applications

Vanadis 30 is a cobalt alloyed high performance PM high speed steel. The cobalt addition of approx. 8,5% has a positive influence on the hot strength/hot hardness, temper resistance and modulus of elasticity. The presence of cobalt has little influence on wear resistance. As cobalt does not form carbides, the wear resistance of Vanadis 30 is more or less the same as for steels with the same base analysis but without cobalt (e.g. Vanadis 23). On the other hand, its presence reduces the toughness and hardenability somewhat but increases compressive strength and high temperature properties.

FOR COLD WORK

- The combination of high wear resistance and unusually good compressive strength can be put to use in tooling for heavy forming operations.
- In some cold work operations, the active surface (e.g. cutting edge or forming surface) of a tool can reach temperatures in excess of 200°C (390°F). Such conditions can be found in tooling running on high speed presses. Also, development of high temperatures in the tooling can be expected in heavy forming operations.

General

Vanadis 30 is a W-Mo-V-Co alloyed PM high speed steel characterized by:

- High wear resistance
- High compressive strength at high hardness
- Good through hardening properties
- Good toughness
- Good dimensional stability on heat treatment
- Good grindability and machinability
- Very good temper resistance.

Typical analysis %	C 1,28	Cr 4,2	Mo 5,0	W 6,4	V 3,1	Co 8,5
Standard specification	(W.-Nr. 1.3207) AISI M2+Co					
Delivery condition	Soft annealed, max. 300 HB Drawn, max. 320 HB					
Colour code	Dark green					

*Punches for high performance.
A suitable application for Vanadis 30.*

Properties


PHYSICAL DATA

Temperature		20°C (68°F)	400°C (750°F)	600°C (1112°F)
Density, kg/m ³ lbs/in ³	(1) (1)	8040 0,287	7935 0,285	7880 0,284
Modulus of elasticity MPa ksi	(2) (2)	240 000 34 x 10 ³	214 000 31 x 10 ³	192 000 28 x 10 ³
Coefficient of thermal expansion per °C from 20°C °F from 68°F	(2) (2)	— —	11,8 x 10 ⁻⁶ 6,5 x 10 ⁻⁶	12,3 x 10 ⁻⁶ 6,8 x 10 ⁻⁶
Thermal conductivity W/m•°C Btu in/(ft ² h•°F)	(2) (2)	22 152	26 180	25 173
Specific heat J/kg °C Btu/lb °F	(2) (2)	420 0,10	510 0,12	600 0,14

(1) = for the soft annealed condition.

(2) = for the hardened and tempered condition.

BEND STRENGTH AND DEFLECTION



Four-point bend testing.


Specimen size: 5 mm (0,2") Ø.

Loading rate: 5 mm/min (0,2"/min.).

Austenitizing temperature: 1050–1180°C (1920–2160°F).

Tempering: 3 x 1 h at 560°C (1040°F), air cooling to room temperature.



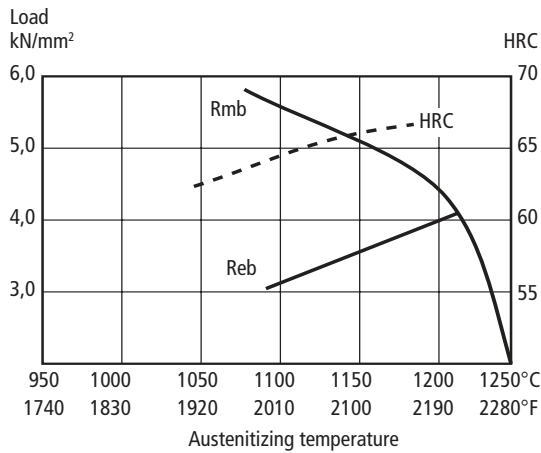

Heat treatment

SOFT ANNEALING

Protect the steel and heat through to 850–900°C (1560–1650°F). Then cool in the furnace at 10°C/h (20°F/h) to 700°C (1290°F), then freely in air.

STRESS RELIEVING

After rough machining the tool should be heated through to 600–700°C (1110–1290°F), holding time 2 hours. Cool slowly to 500°C (930°F), then freely in air.

HARDENING


Pre-heating temperature: 450–500°C (840–930°F) and 850–900°C (1560–1650°F).

Austenitizing temperature: 1050–1180°C (1920–2160°F), according to the desired final hardness, see diagram below.

The tool should be protected against decarburization and oxidation during hardening.


Hardness after tempering 3 times for one hour at 560°C (1040°F)

Final hardness HRC

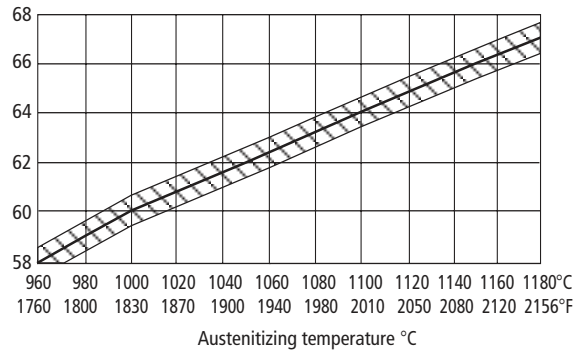

HIGH TEMPERATURE PROPERTIES


Vanadis 30 hot hardness

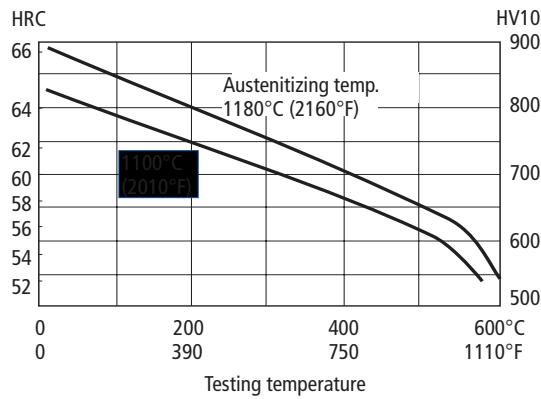

Change in hardness versus holding time for different working temperatures

Austenitizing temperature: 1050–1130°C (1920–2070°F).


Tempering: 3 x 1 h at 560°C (1040°F).

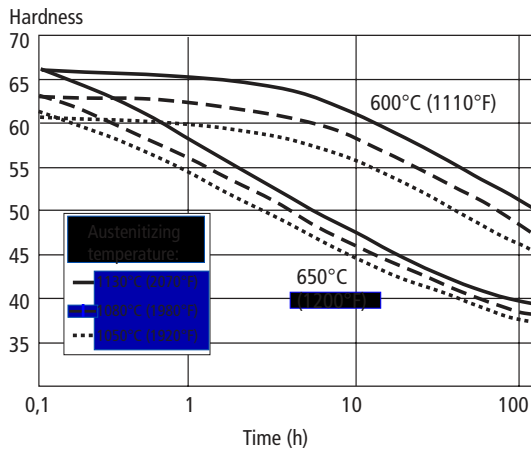

Hardness for different austenitizing temperatures after tempering 3 times for one hour at 560°C (± 1 HRC)


HRC	°C	°F
60	1000	1832
62	1050	1922
64	1100	2012
66	1150	2102
67	1180	2156

Recommended holding time

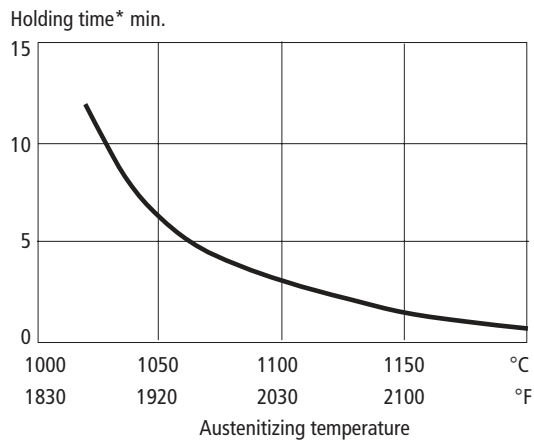


* Holding time = time at austenitizing temperature after the tool is fully heated through.

Total soaking time in a salt bath after pre-heating in two stages at 450°C (840°F) and 850°C (1560°F)

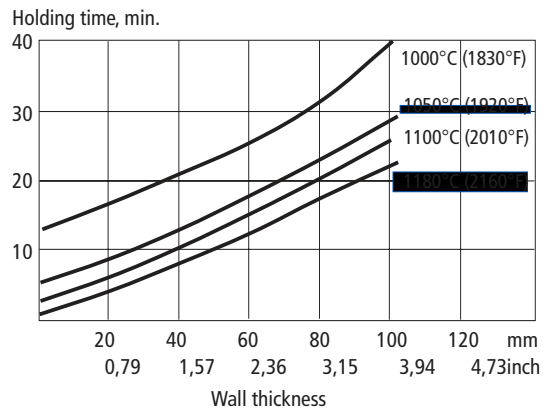

CCT-graph (continuous cooling)

Austenitizing temperature 1180°C (2160°F).

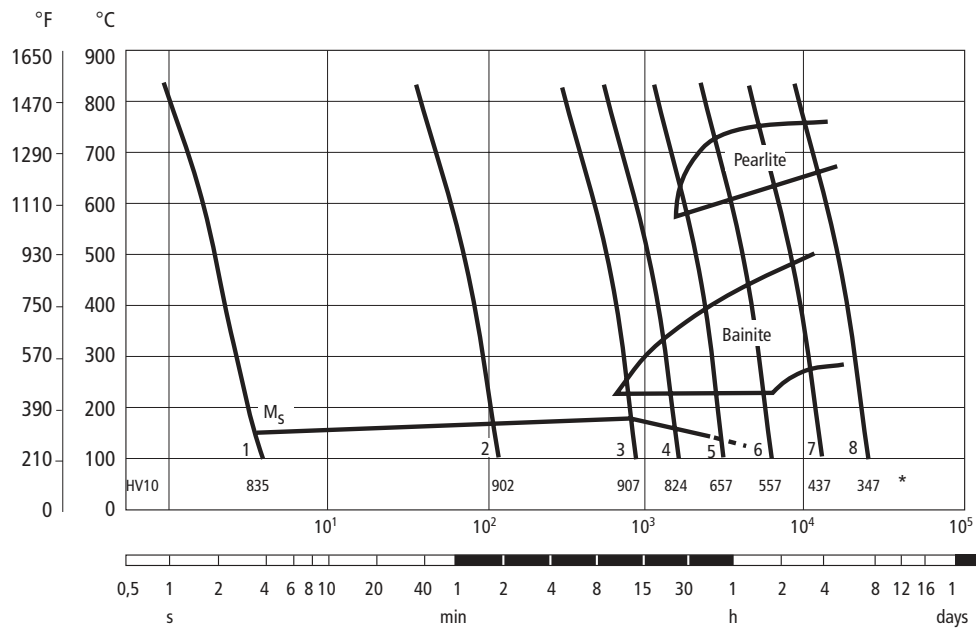

QUENCHING MEDIA

- Martempering bath at approx. 540°C (1004°F)
- Vacuum furnace with high speed gas at sufficient overpressure.

Note. 1: Quenching should be continued until the temperature of the tool reaches approx. 50°C (122°F). The tool should then be tempered immediately.

Note. 2: In order to obtain a high toughness, the cooling speed in the core should be at least 10°C/sec. (20°F/sec.). This is valid for cooling from the austenitizing temperature down to approx. 540°C (1004°F). After temperature equalization between the surface and core, the cooling rate of approx. 5°C/sec. (10°F/sec.) can be used. The above cooling cycle results in less distortion and residual stresses.

TEMPERING

Tempering should always be carried out at 560°C (1040°F) irrespective of the austenitizing temperature. Temper three times for one hour at full temperature. The tool should be cooled to room temperature between the tempers. The retained austenite content will be less than 1% after this tempering cycle.

DIMENSIONAL CHANGES

Dimensional changes after hardening and tempering.

Heat treatment: austenitizing between 1050–1140°C (1920–2080°F) and tempering 3 x 1h at 560°C (1040°F).

Specimen size: 80 x 80 x 80 mm (2,91 x 2,91 x 2,91 in.) and 100 x 100 x 25 mm (3,94 x 3,94 x 0,99 in.).

Dimensional changes: growth in length, width and thickness: +0,03% to +0,13%.


Surface treatments

Some tools are given a surface treatment in order to reduce friction and increase tool wear resistance. The most commonly used treatments are nitriding and surface coating with wear resistant layers of titanium carbide and titanium nitride (CVD, PVD).

Vanadis 30 has been found to be particularly suitable for titanium carbide and titanium nitride coatings. The uniform carbide distribution in Vanadis 30 facilitates bonding of the coating and reduces the spread of dimensional changes resulting from hardening. This, together with its high strength and toughness, makes Vanadis 30 an ideal substrate for high-wear surface coatings.

NITRIDING

A brief immersion in a special salt bath to produce a nitrided diffusion zone of 2–20 µm is recommended. This reduces friction on the envelope surface of punches and has various other advantages.

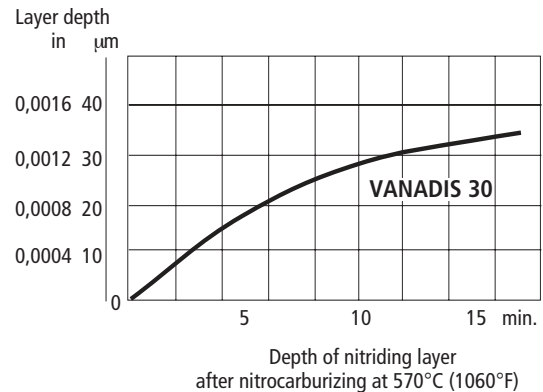

PVD

Physical vapour deposition, PVD, is a method of applying a wear-resistant coating at temperatures between 200–500°C (390–930°F). As Vanadis 30 is high temperature tempered at 560°C (1040°F), there is no danger of dimensional changes during PVD coating.

CVD

Chemical vapour deposition, CVD, is used for applying wear resistant surface coatings at a temperature of around 1000°C (1830°F). It is recommended that the tools should be separately hardened and tempered in a vacuum furnace after surface treatment.

Cutting data recommendations

The cutting data below are to be considered as guiding values which must be adapted to existing local conditions. More information can be found in the Uddeholm publication "Cutting data recommendations"

Condition: Soft annealed to approx. 300 HB

TURNING

Cutting data parameters	Turning with carbide		Turning with HSS Fine turning
	Rough turning	Fine turning	
Cutting speed (v_c) m/min f.p.m.	80–110 262–361	110–140 361–459	10–15 33–49
Feed (f) mm/r i.p.r.	0,2–0,4 0,008–0,016	0,05–0,2 0,002–0,008	0,05–0,3 0,002–0,012
Depth of cut (a_p) mm inch	2–4 0,08–0,16	0,5–2 0,02–0,08	0,5–3 0,02–0,12
Carbide designation ISO	K20, P10–P20 Coated carbide*	K15, P10 Coated carbide*	–

* Use a wear resistant CVD-coated carbide grade

DRILLING

High speed steel twist drill

Drill diameter		Cutting speed v_c		Feed f	
mm	inch	m/min.	f.p.m.	mm/r	i.p.r.
– 5	–3/16	8–10*	27–33*	0,05–0,15	0,002–0,006
5–10	3/16–3/8	8–10*	27–33*	0,15–0,20	0,006–0,008
10–15	3/8–5/8	8–10*	27–33*	0,20–0,25	0,008–0,010
15–20	5/8–3/4	8–10*	27–33*	0,25–0,35	0,010–0,014

For coated HSS drill $v_c = 14–16$ m/min. (46–52 f.p.m.)

Carbide drill

Cutting data parameters	Type of drill		
	Indexable insert	Solid carbide	Brazed carbide ¹⁾
Cutting speed, v_c m/min f.p.m.	100–130 328–435	50–70 164–230	25–35 82–115
Feed, f mm/r i.p.r.	0,05–0,15 ²⁾ 0,002–0,006 ²⁾	0,10–0,25 ²⁾ 0,004–0,010 ²⁾	0,15–0,25 ²⁾ 0,006–0,010 ²⁾

¹⁾ Drill with internal cooling channels and brazed tip.

²⁾ Depending on drill diameter.

MILLING

Face and square shoulder milling

Cutting data parameters	Milling with carbide	
	Rough milling	Fine milling
Cutting speed (v_c) m/min f.p.m.	40–80 131–265	80–110 265–361
Feed (f_z) mm/tooth inch/tooth	0,2–0,4 0,008–0,016	0,1–0,2 0,004–0,008
Depth of cut (a_p) mm inch	2–4 0,08–0,16	–2 –0,08
Carbide designation ISO	K20–P20 Coated carbide*	K15–P15 Coated carbide* or cermet

* Use a wear resistant CVD-coated carbide grade

End milling

Cutting data parameters	Type of mill		
	Solid carbide	Carbide indexable insert	High ²⁾ speed steel
Cutting speed (v_c) m/min f.p.m.	35–45 115–150	70–90 230–300	12–16 39–52
Feed (f_z) mm/tooth inch/tooth	0,01–0,2 ¹⁾ 0,0004–0,008 ¹⁾	0,06–0,2 ¹⁾ 0,002–0,008 ¹⁾	0,01–0,3 ¹⁾ 0,0004–0,012 ¹⁾
Carbide designation ISO	–	K15, P10–P20 Coated carbide ³⁾	–

¹⁾ Depending on radial depth of cut and cutter diameter.

²⁾ Uncoated high speed steel mill is not recommended

³⁾ Use a wear resistant CVD-coated carbide grade

GRINDING

General grinding wheel recommendation is given below. More information can be found in the Uddeholm publication "Grinding of Tool Steel".

Type of grinding	Annealed condition	Hardened condition
Face grinding straight wheel	A 46 HV	B151 R50 B3 ¹⁾ A 46 HV ²⁾
Face grinding segments	A 36 GV	A 46 GV
Cylindrical grinding	A 60 KV	B151 R50 B3 ¹⁾ A 60 KV ²⁾
Internal grinding	A 60 JV	B151 R75 B3 ¹⁾ A 60 IV
Profile grinding	A 100 JV	B126 R100 B6 ¹⁾ A 120 JV ²⁾

¹⁾ If possible use CBN wheels for this application.

²⁾ Preferable a wheel type containing sintered Al_2O_3 (seeded gel)

EDM

If EDM is performed in the hardened and tempered condition, finish with "finesparking", i.e. low current, high frequency. For optimal performance the EDM'd surface should then be ground/polished and the tool retempered at approx. 535°C (995°F).

Further information

Please, contact your local Uddeholm office for further information on the selection, heat treatment, application and availability of Uddeholm tool steels.

Relative comparison of Uddeholm cold work tool steels

MATERIAL PROPERTIES AND RESISTANCE TO FAILURE MECHANISMS

Uddeholm grade	Hardness/ Resistance to plastic deformation	Machinability	Grindability	Dimension stability	Resistance to		Fatigue cracking resistance	
					Abrasive wear	Adhesive wear	Ductility/ resistance to chipping	Toughness/ gross cracking
ARNE	████	██████	██████	█	████	████	████	████
CALMAX	████	██████	██████	██████	████	████	██████	██████
CALDIE	██████	██████	██████	██████	████	██████	██████	██████
RIGOR	████	██████	████	██████	████	████	████	████
SLEIPNER	██████	██████	████	██████	██████	██████	████	████
SVERKER 21	████	██████	██	██████	██████	██	██	████
SVERKER 3	████	██	█	██████	██████	██	██	██
VANADIS 4 Extra	██████	██████	████	██████	██████	██████	██████	████
VANADIS 6	██████	██	██	██████	██████	██████	████	██
VANADIS 10	██████	██	██	██████	██████	██████	████	██
VANADIS 23	██████	████	████	██████	██████	██████	████	████
VANADIS 30	██████	████	████	██████	██████	██████	██	████
VANADIS 60	██████	██	██	██████	██████	██████	██	████
AISI M:2	██████	████	████	██████	██████	████	██	██

UDDEHOLM EUROPE**AUSTRIA**

UDDEHOLM
Hansaallee 321
D-40549 Düsseldorf
Telephone: +49 211 535 10
Telefax: +49 211 535 12 80

BELGIUM

UDDEHOLM N.V.
Waterstraat 4
B-9160 Lokeren
Telephone: +32 9 349 11 00
Telefax: +32 9 349 11 11

CROATIA

BOHLER UDDEHOLM Zagreb
d.o.o. za trgovinu
Zitnjak b.b.
10000 Zagreb
Telephone: +385 1 2459 301
Telefax: +385 1 2406 790

CZECHIA

BOHLER UDDEHOLM CZ s.r.o.
Division Uddeholm
U silnice 949
161 00 Praha 6 Ruzyně
Czech Republic
Telephone: +420 233 029 850,8
Telefax: +420 233 029 859

DENMARK

UDDEHOLM A/S
Kokmose 8, Bramdrupdam
DK-6000 Kolding
Telephone: +45 75 51 70 66
Telefax: +45 75 51 70 44

ESTONIA

UDDEHOLM TOOLING ESTI OÜ
Silikatsiidi 7
EE-11216 Tallinn, Estonia
Telephone: +372 655 9180
Telefax: +372 655 9181

FINLAND

OY UDDEHOLM AB
Ritakuja 1, PL 57,
FIN-01741 VANTAA
Telephone: +358 9 290 490
Telefax: +358 9 2904 9249

FRANCE

UDDEHOLM S.A.
12 Rue Mercier, Z.I. de Mitry-Compans
F-77297 Mitry Mory Cedex
Telephone: +33 (0)1 60 93 80 10
Telefax: +33 (0)1 60 93 80 01

Branch office

UDDEHOLM S.A.
77bis, rue de Vesoul
La Nef aux Métiers
F-25000 Besançon
Telephone: +33 381 53 12 19
Telefax: +33 381 53 13 20

GERMANY

UDDEHOLM
Hansaallee 321
D-40549 Düsseldorf
Telephone: +49 211 535 10
Telefax: +49 211 535 12 80

Branch offices

UDDEHOLM
Falkenstraße 21
D-65812 Bad Soden/TS.
Telephone: +49 6196 659 60
Telefax: +49 6196 659 625

UDDEHOLM

Albstraße 10
D-73765 Neuhausen
Telephone: +49 715 898 65-0
Telefax: +49 715 898 65-25

GREAT BRITAIN, IRELAND

UDDEHOLM UK LIMITED
European Business Park
Taylors Lane, Oldbury
West Midlands B69 2BN
Telephone: +44 121 552 55 11
Telefax: +44 121 544 29 11

Dublin Telephone: +353 1 45 14 01

GREECE

UDDEHOLM STEEL TRADING
COMPANY
20, Athinon Street
G-Piraeus 18540
Telephone: +30 2 10 41 72 109/41 29 820
Telefax: +30 2 10 41 72 767

Agency

SKLERO S.A.
Steel Trading Comp. and
Hardening Shop
Frixou 11/Nikif. Ouranou
G-54627 Thessaloniki
Telephone: +30 31 51 46 77
Telefax +30 31 54 12 50

SKLERO S.A.
Heat Treatment and Trading of Steel
Uddeholm Tool Steels
Industrial Area of Thessaloniki
P.O. Box 1123
G-57022 Sindos, Thessaloniki
Telephone: +30 23 10 79 76 46
Telefax: +30 23 10 79 76 78

HUNGARY

UDDEHOLM TOOLING/BOK
Dunaharaszti, Jedlik Ányos út 25
H-2331 Dunaharaszti 1.Pf. 110
Telephone/Telefax: +36 24 492 690

ITALY

UDDEHOLM div. della Bohler
Uddeholm Italia S.p.A.
Via Palizzi, 90
I-20157 Milano
Telephone: +39 02 35 79 41
Telefax: +39 02 390 024 82

LATVIA

UDDEHOLM TOOLING AB
Piedrujas street 7
LV-1037 Riga, Latvia
Telephone: +371 7 701 983, -981, -982
Telefax: +371 7 147 373

LITHUANIA

UDDEHOLM TOOLING AB
BE PLIENAS IR METALAI
T. Masiulio 18b
LT-52459 Kaunas
Telephone: +370 37 370613, -669
Telefax: +370 37 370300

THE NETHERLANDS

UDDEHOLM B.V.
Isolatorweg 30
NL-1014 AS Amsterdam
Telephone: +31 20 581 71 11
Telefax: +31 20 684 86 13

NORWAY

UDDEHOLM A/S
Jernkroken 18
Postboks 85, Kalbakken
N-0902 Oslo
Telephone: +47 22 91 80 00
Telefax: +47 22 91 80 01

POLAND

INTER STAL CENTRUM
Sp. z o.o./Co. Ltd.
ul. Kolejowa 291, Dziekanów Polski
PL-05-092 Lomianki
Telephone: +48 22 429 2260
Telefax: +48 22 429 2266

PORTUGAL

F RAMADA Aços e Industrias S.A.
P.O. Box 10
P-3881 Ovar Codex
Telephone: +351 56 58 61 11
Telefax: +351 56 58 60 24

ROMANIA

BÖHLER Romania SRL
Uddeholm Branch
Str. Atomistilor Nr 14A
077125 Magurele Jud Ilfov
Telephone: +40 214 575007
Telefax: +40 214 574212

RUSSIA

UDDEHOLM TOOLING CIS
25 A Bolshoy pr PS
197198 St. Petersburg
Telephone: +7 812 233 9683
Telefax: +7 812 232 4679

SLOVAKIA

UDDEHOLM Slovakia
Nástrojové ocele, s.r.o
KRÁČINY 2
036 01 Martin
Telephone: +421 842 4 300 823
Telefax: +421 842 4 224 028

SLOVENIA

UDDEHOLM div. della Bohler
Uddeholm Italia S.p.A.
Via Palizzi, 90
I-20157 Milano
Telephone: +39 02 35 79 41
Telefax: +39 02 390 024 82

SPAIN

UDDEHOLM
Guifré 690-692
E-08918 Badalona, Barcelona
Telephone: +34 93 460 1227
Telefax: +34 93 460 0558

Branch office

UDDEHOLM
Barrio San Martin de Arteaga, 132
Pol.Ind. Torrelarragoiti
E-48170 Zamudio
(Bizkaia)
Telephone: +34 94 452 13 03
Telefax: +34 94 452 13 58

SWEDEN

UDDEHOLM TOOLING
SVENSKA AB
Aminogatan 25
SE-431 53 Mölndal
Telephone: +46 31 67 98 50
Telefax: +46 31 27 02 94

SWITZERLAND

HERTSCH & CIE AG
General Wille Strasse 19
CH-8027 Zürich
Telephone: +41 44 208 16 66
Telefax: +41 44 201 46 15

**UDDEHOLM
NORTH AMERICA****USA**

UDDEHOLM
4902 Tollview Drive
Rolling Meadows, IL 60008
Sales Phone: +1 800 638 2520
Sales Fax: +1 630 350 0880

Region East Warehouse
UDDEHOLM – Shrewsbury, MA

Region Central Warehouse
UDDEHOLM – Wood Dale, IL

Region West Warehouse
UDDEHOLM – Santa Fe Springs, CA

CANADA

UDDEHOLM
2595 Meadowvale Blvd.
Mississauga, ON L5N 7Y3
Telephone: +1 905 812 9440
Telefax: +1 905 812 8658

Branch Warehouses
UDDEHOLM – St. Laurent, QC
UDDEHOLM – New Westminster, BC

Heat Treating
THERMO-TECH – Mississauga, ON

MEXICO

ACEROS BOHLER UDDEHOLM,
S.A. de C.V.
Calle 8 No 2, Letra C
Fraccionamiento Industrial Alce Blanco
C.P. 52787 Naulcapan de Juarez
Estado de Mexico
Telephone: +52 55 9172 0242
Telefax: +52 55 5576 6837

UDDEHOLM

Letrado de Tejada No.542
Colonia Las Villas
66420 San Nicolas de Los Garza, N.L.
Telephone: +52 8-352 5239
Telefax: +52 8-352 5356

**UDDEHOLM
SOUTH AMERICA****ARGENTINA**

UDDEHOLM S.A
Mozart 40
1619-Centro Industrial Garin
Garin-Prov. Buenos Aires
Telephone: +54 332 744 4440
Telefax: +54 332 745 3222

BRAZIL

UDDEHOLM ACOS ESPECIAIS Ltda.
Estrada Yae Massumoto, 353
CEP 09842-160
Sao Bernardo do Campo - SP Brazil
Telephone: +55 11 4393 4560, -4554
Telefax: +55 11 4393 4561

**UDDEHOLM
SOUTH AFRICA**

UDDEHOLM Africa (Pty) Ltd.
P.O. Box 539
ZA-1600 Isando/Johannesburg
Telephone: +27 11-974 2781
Telefax: +27 11-392 2486

**UDDEHOLM
AUSTRALIA**

BOHLER-UDDEHOLM Australia
129-135 McCredie Road
Guildford NSW 2161
Private Bag 14
Telephone: +61 2 9681 3100
Telefax: +61 2 9632 6161

Branch offices

Sydney, Melbourne, Adelaide,
Brisbane, Perth, Newcastle,
Launceston, Albury, Townsville

ASSAB**ASSAB INTERNATIONAL**

Skytteholmsvägen 2
P O Box 42
SE-171 11 Solna
Sweden
Telephone: +46 8 564 616 70
Telefax: +46 8 25 02 37

Subsidiaries

India, Iran, Turkey, United Arab
Emirates, Saudi Arabia
Distributors in
Africa, Latin America, Middle East

ASSAB PACIFIC

ASSAB Pacific Pte. Ltd
171, Chin Swee Road
No. 07-02, San Centre
Singapore 169877
Telephone: +65 534 56 00
Telefax: +65 534 06 55

Subsidiaries

China, Hong Kong, Indonesia, Japan,
Korea, Malaysia, Philippine Islands,
Singapore, Taiwan, Thailand

When the first idea pops into your head, throughout the development process to the release of the new product, we'll be your partner. As the world's leading supplier of tooling materials and related services, we can be trusted. Meet us under the Uddeholm and ASSAB brands, wherever in the world you have your business.

